

**EXPERIMENTAL OPTIMIZATION OF MILD STEEL ON TIG  
WELDING**

A Thesis

Submitted

In Partial Fulfillment of the Requirements

for the Degree of

**MASTER OF TECHNOLOGY**

In

**Production and Industrial Engineering**

Submitted by

**Sheet Kumar**

Under the Supervision of

**Dr. Mohd. Shadab Khan**

**(Associate Professor)**



Department of Mechanical Engineering

Faculty of Engineering

**INTEGRAL UNIVERSITY, LUCKNOW, INDIA**

July, 2022



# INTEGRAL UNIVERSITY

## इंटीग्रल विश्वविद्यालय

Accredited by NAAC. Approved by the University Grants Commission under Sections 2(f) and 12B of the UGC Act, 1956, MCI, PCI, IAP, BCI, INC, CoA, NCTE, DEB & UPSMF. Member of AIU. Recognized as a Scientific & Industrial Research Organization (SIRO) by the Dept. of Scientific and Industrial Research, Ministry of Science & Technology, Government of India.

### CERTIFICATE

This is to secure that this is work eligible “**EXPERIMENTAL OPTIMIZATION OF MILD STEEL ON TIG WELDING**” submitted by **Mr. Sheet Kumar (Enroll.No.07001160585)** in partial fulfillment for grant of Master of Technology in Mechanical Engineering Department with specialization in Mechanical Engineering (**Production and Industrial Engineering**), to **INTEGRAL UNIVERSITY, Lucknow (U.P.)**. He has done his work under my superintendence and direction and superior insight; the issue encapsulated in this proposition has not been present to some other University/Institute for honor of any masters-degree to the hopeful or to any other person.

Signature of Supervisor

Full Name: **Dr. Mohd Shadab Khan,**

Designation: Associate Professor,

Department of Mechanical Engineering

Address: Integral University, Lucknow.

Date:

Place:

### **CANDIDATE'S DECLARATION**

I hereby declare that the work which is being presented in the thesis entitled **EXPERIMENTAL OPTIMIZATION OF MILD STEEL ON TIG WELDING**", submitted to the Dept. of Mechanical Engineering, **INTEGRAL UNIVERSITY, Lucknow (U.P.)**, India for award of degree of Master of Technology in Mechanical Engineering(**Production and Industrial Engineering**), is an authentic record of my own work carried out during my M.tech course under the supervision of**Dr. Mohd Shadab Khan**.

I have not submitted the matter presented in the thesis for the award of any other degree of this or any other university.

**Sheet Kumar**

**Enroll. No: 07001160585**

## **ABSTRACT**

Tungsten Inert Gas welding is otherwise called Gas Tungsten Arc Welding (GTAW), is a development bend welding process become a mainstream decision when a significant level of weld quality or extensive accuracy welding is required. In any case, the serious issues of TIG welding process are its moderate welding pace and constrained to bring down thickness material in single pass. In this work, autogenous TIG welding has been performed on 5 mm thick AISI 1020 mellow steel plate without utilizing any filler material. Wide scope of welding current and output speed has been tried for acquiring a full infiltration welding. Enacted transition has likewise been utilized to improve the weld profundity. In the wake of performing welding by keeping up various holes between the plates to be welded, weld dab geometry and rigidity of the weld has been explored. It is seen that, by keeping up a proper whole full infiltration welding of plate is conceivable which invigorates practically like base material.

Austenitic stainless steels are widely used in the application of aircraft engine parts, heat exchangers, furnace parts etc. It contains both chromium and nickel. Nickel and chromium aids stability of austenite over wide range of temperatures and high corrosion resistance respectively. 316L austenitic stainless steel is low carbon (0.03%) steel, developed from 316 austenitic stainless steel and contains carbon (0.08%). The causes of decreased contents of carbon, minimizes the problem of harmful carbide precipitation during welding. Activated Tungsten Inert Gas (A-TIG) welding can increase the joint penetration and weld depth-width ratio, thereby reducing angular distortion of the weldment. This paper address the A-TIG welding, and their significance & advantages.

In this paper, Tungsten Inert Gas (TIG) Welding with the welding speed is controlled by the microcontroller for the purpose of adjusting the back bead width has observed. The back bead

width is estimated based on data of weld bead width obtained from machine vision, welding speed, and currents that used in this experimental. It's used to obtain a series of data which would have conducted as initial experiments to train and build the neural network system. Results showed that the back bead width is 3 mm on the current 55 A, 60 A, and 65 A have an average error of each current of 0.11 mm, 0.09 mm, and 0.12 mm.

**Watchwords** - Tungsten Inert Gas welding, Activated motion, Tensile test, Hardness test and A  
- TIG welding process.

## ACKNOWLEDGEMENT

I might want to emphasize my intense feeling of apprehension and regard to my supervisor **Dr. Mohd Shadab Khan** for his significant direction, inspiration and motivation and for his involvement in order to raise this theory in introduce frame. I see myself privileged to have the capacity to work under the direction of such an inducement identity.

I am also thankful to **Dr. P.K. Bharti** Head of Department, Mechanical Engineering, for his indorse and motivation.

My special thanks all my relatives. Their adoration, friendship and persistence made this work conceivable and favors of my dearest guardians significantly sub serve me doing this research work.

Place: LUCKNOW

Date:

## TABLE OF CONTENTS

<b>Content</b>	<b>Page No.</b>
TITLE PAGE	i
CERTIFICATE	ii
CANDIDATE'S DECLARATION	iii
ABSTRACT	iv
ACKNOWLEDGEMENT	vi
TABLE OF CONTENT	vii
LIST OF TABLE	ix
LIST OF FIGURE	x
<b>CHAPTER 1: INTRODUCTION</b>	
1.1 Classification of Welding processes	1
1.2 Tungsten Inert Gas welding	2
1.2.1 Principle of TIG welding	3
1.2.2 Advantages of TIG welding process	3
1.2.3 Disadvantages of TIG welding process	4
1.3 Welding process parameters of TIG welding	4
1.4 Autogenous TIG welding	5
<b>CHAPTER 2: LITERATURE REVIEW</b>	
2.1 Motivation and objective of present work	7
<b>CHAPTER 3: METHODOLOGY</b>	
3.1 Experimental setup	14
<b>CHAPTER 4: EXPERIMENTATION</b>	
4.1 Single pass TIG welding on mild steel plate	18
4.1.1 Sample preparation for study the weld bead geometry	19
4.1.2 TIG welding process with TiO <sub>2</sub> Flux	20
4.1.3 TIG welding of mild steel by varying gap between workpieces to bewelded	21
<b>CHAPTER 5: RESULT AND DISCUSSION</b>	
5.1 Welded specimen performed by conventional autogenous TIG welding	23

5.1.1 Optical Image at weld zone by conventional autogenous TIG welding processes	24
5.1.2 Weld bead geometry at cross section of weld zone by conventional autogenous TIG Welding	25
5.2 Welded specimen performed by activated TIG welding process	26
5.2.1 Optical Image at weld zone of specimen performed by activated TIGwelding process	27
5.2.2 Weld bead geometry at cross section of weld zone by TIG welding with TiO <sub>2</sub> flux	29
5.3 Welded specimen performed by welding by varying gap between work piece	30
5.4 Tensile testing	36
5.5 Vickers Hardness test	39
<b>CHAPTER 6: CONCLUSIONS</b>	
6.1 Future Aspects	41
<b>CHAPTER 7: REFERENCES</b>	<b>42</b>



## List of Tables

<b>Tables</b>	<b>Page No.</b>
Table 1: Welding parameters for autogenous TIG welding of mild steel	18
Table 2: Experimental planning for autogenous TIG welding of mild steel	19
Table 3: Dimension for tensile test as per ASTM E8 standard	
Table 4: Welding parameters for TIG welding of TiO <sub>2</sub> flux coated mild steel	21
Table 5: Experimental planning for TIG welding of mild steel	22
Table 6: Width and depth of weld zone of TIG welded sample by conventional TIG welding	25
Table 7: Width and depth of weld zone of TIG welding with TiO <sub>2</sub> flux	
Table 8: Comparison of depth of penetration between without flux weld and with flux weld sample	30
Table 9: Measurement of width, depth and crater of welded sample at weld zone for different current and gap maintained between workpiece	32
Table 10: Tensile strength at weld joint by TIG welding of varying gap between work piece	37
Table 11: Hardness value for sample	39

## LIST OF FIGURES

<b>Figures</b>	<b>Page No.</b>
Fig. 1: Schematic Diagram of working principle of TIG Welding	6
Fig. 2: Experimental setup of TIG welding	15
Fig. 3: Welding torch	16
Fig. 4: INSTRON Universal Testing Machine (UTM)	20
Fig. 5: Welded specimens performed with 3 different speed and current setting by conventional autogenous TIG welding process	23
Fig. 6: Optical microscopic Image at cross section of weld by conventional autogenous TIG welding process	24
Fig. 7: Variation of weld bead width against scan speed for different welding current	25
Fig. 8: Variation of weld pool depth against scan speed for different welding current	26
Fig. 9: TIG welded specimen with TiO <sub>2</sub> flux at 210 A current	27
Fig. 10: Optical microscopic Image at weld zone of TIG welded specimen with use of TiO <sub>2</sub> flux	27
Fig. 11: Variation of weld bead width against scan speed for 210 A welding current	28
Fig. 12: Variation of weld pool depth against scan speed for 210 A welding current	29
Fig. 13: TIG welded specimens by varying gap between workpiece	31
Fig. 14: Optical microscopic Image at weld zone of TIG welding done with different welding current and gap between workpiece	
Fig. 15: Variation of weld pool depth against welding current for different gap between workpiece to be welded	32
Fig. 16: Variation of weld pool depth against gap between workpiece to be welded for different welding current	33
Fig. 17: Variation of weld bead width against welding current for different gap between workpiece to be welded	34
Fig. 18: Variation of weld bead width against gap between workpiece to be welded for different welding current	35

Fig. 19: Variation of weld crater against welding current for different gap between workpiece to be welded	35
Fig. 20: Variation of weld crater against gap between workpiece to be welded for different welding current	36
Fig. 21: Tensile testing specimen	
Fig. 22: Variation of tensile strength against gap between workpiece to be welded for different welding current	38
Fig. 23: Variation of tensile strength against welding current for different gap between workpiece to be welded	38
Fig. 24: Hardness value of sample at weld zone processed with 200 A current and 0.75 mm gap	39

# CHAPTER 1

## INTRODUCTION

Welding is a process of joining two similar or dissimilar metals by fusion, with or without application of pressure and with or without use of filler metal. Weldability of the material depends upon various factors like the metallurgical changes that occur due to welding, change in hardness of material, in and around the weld and the extent of cracking tendency of the joint. A range of welding processes have been developed so far using single or combination of factors like pressure, heat and filler material used.

### **1.1 Classification of Welding processes**

- I. Homogeneous welding
  - II. Heterogeneous welding
  - III. Autogenous welding
- I. Homogeneous welding – Welding of thick plates using filler metal used as per needs according to thickness of plate. The filler material used to provide better strength to the joint. In this process filler material is same as base metal. Different types of homogeneous welding process commonly used are:
- a) Arc welding – Filler material generally used as consumable electrode for manual arc welding and metal inert gas welding.
  - b) Gas welding – An external filler rod is required for gas welding.
  - c) Plasma arc welding – In case of Plasma arc welding also an external filler rod is necessary for welding.
  - d) Thermit welding – In case of thermit welding a molten material from some chemical reaction is added.

In case of homogeneous welding solidification occurs directly by growth mechanism without nucleation stage.

II. Heterogeneous welding – A filler material different from the base material is used for welding. The solidification in heterogeneous weld takes place in two stages *i.e.* nucleation and growth.

Since, Homogeneous and Heterogeneous welding process required external filler material therefore an arrangement for this filler rod feeding (in case of automated system) make the process complex and costly.

III. Autogenous welding – A weld joint can be developed just by melting of edges of plates or sheets. This type of welding used especially if plate thickness is less than 5 mm. No filler is added during autogenous welding. All types of solid phase welding, resistance welding and fusion welding without filler rod corresponding thin category of welding are examples of this category. Following are the some specific advantages of autogenous welding process:

- Suitable for high production rate.
- Heating of the workpiece is confined to very small parts which results in less distortion.
- Possible to weld dissimilar metals as well metal plates of different thickness.
- High speed welding is possible.
- Since no external material is used, the process is very economical.
- Since no filler rod is used, process can be automated easily.

## **1.2 Tungsten Inert Gaswelding**

Tungsten Inert Gas welding is also known as Gas tungsten arc welding (GTAW), is arc welding process that use non-consumable tungsten electrode to produce arc. The welded area is protected from atmospheric contamination by an inert shielding gas (argon or helium), and a

filler is normally used to weld thick plate. The electrode is non consumable since its melting point is about 3400°C. In tungsten electrode 1 to 2% thorium and zirconium are added to improve electron emission, arc stability and current carrying capacity. A constant current welding power supply produces energy which is conducted across the arc through a column of highly ionized gas and metal vapors known as plasma. Heat input in GTAW does not depend on the filler material rate. Consequently, the process allows a precise control of heat addition and the production of superior quality welds, with low distortion and free of spatter.

### **1.2.1 Principle of TIG welding**

In TIG welding process, the electrode is non consumable and purpose of it only to create an arc. The heat-affected zone, molten metal and tungsten electrode are all shielded from atmospheric contamination by a blanket of inert gas fed through the GTAW torch. Fig. 1 shows schematic diagram of the working principle of TIG welding process. Welding torch consist of light weight handle, with provision for holding a stationary tungsten electrode. In the welding torch, the shielding gas flows by or along the electrode through a nozzle into arc region. An electric arc is created between electrode and the workpiece material using a constant current welding power source to produce energy and conducted across the arc through a column of highly ionized gas and metal vapors. The electric arc produce high temperature and heat can be focused to melt and join two different parts of workpiece.

### **1.2.2 Advantages of TIG welding process**

- Concentrated arc produced for control heat input to the workpiece. It resulting in a narrow heat-affected zone.
- This process is done without use of flux, therefore no slag formation during welding process.
- No Sparks or Spatter because of no transfer of metal across the arc during TIG welding.

- Compared to other arc welding processes like flux cored welding, fewer amounts of fumes or smokes are produced.
- Welding of thin material is possible.
- Welding dissimilar type material is possible.
- Welding of different types of metal and metal alloys are possible by proper control
- Welding of different types of metal and metal alloys is possible.

### **1.2.3 Disadvantages of TIG welding process**

- Low travel speeds than other welding processes to make the process slow.
- Low filler material deposition during welding compare to other arc welding process.
- High skills are required for manual welding process.
- Welding equipment cost is higher than other arc welding process.

### **1.3 Welding process parameters of TIG welding**

1. Welding current – Constant current type power source are used for TIG welding process.

The preferred polarity for TIG welding process depends upon the type of workpiece material being welded. Direct Current (DC) with straight polarity is used for Cu alloy and stainless steel. DC with reverse polarity is used for magnesium. The Alternating Current (AC) is more versatile in welding for steel and aluminium. Fixed current mode varies the voltage to maintain a constant arc current.

2. Arc voltage - This can be fixed or adjustable depending on the equipment used for TIG welding. Some metals require a specific voltage range for welding. A high initial voltage is required for easy arc initiation. It also allows for a greater range of working tip distance between electrode and workpiece. Too large voltage, can lead to greater variability in workpiece quality.

5. Shielding Gas – Shielding gas is required for TIG welding to protect weld area from

atmospheric contamination. If atmospheric gases (oxygen and nitrogen) are come in contact with tungsten electrode, arc or welding metal cause fusion defect and porosity. Various shielding gases are available including mixtures of argon, helium and hydrogen. Mostly argon is used as a shielding gas for TIG welding. The choices of shielding gas affect depth of penetration, surface weld profile, strength, brittleness and hardness.

4. Gas flow rate – A uniform flow of inert gas is required to shield the molten metal. Gas flow rate can vary, proper selection of flow rate is required for ensure weld quality and improve efficiency. The value of gas flow rate is dependent on the thickness of the workpiece material to be welded. Lower flow rate required for manual welding than automatic welding process.


5. Welding speed – The amount of energy transferred per unit length of weld is inversely proportional to the welding speed. Maximum value of welding current with low speed provides maximum heat energy to the weld. Compare with the high welding speed in TIG welding low welding speed reduces the tendency of porosity.

#### **1.4 Autogenous TIG welding**

A weld joint produced by melting the contact edge surfaces and subsequently solidifying it at room temperature (without addition of any filler metal) is called “autogenous weld”. Thus, the composition of the autogenous weld metal corresponds to the base metal only. However, autogenous weld is crack sensitive when solidification temperature range of the base metal to be welded is significantly high. TIG welding process performed without application of filler material is known as autogenous TIG welding process. Autogenous TIG welding is preferred especially for less than 5 mm thick plate. The advantages of this process are that, it is economical process as compare to heterogeneous or homogenous welding process as no edge preparation and filler material are required. Figure 2 shows schematic diagram of autogenous TIG welding



process.

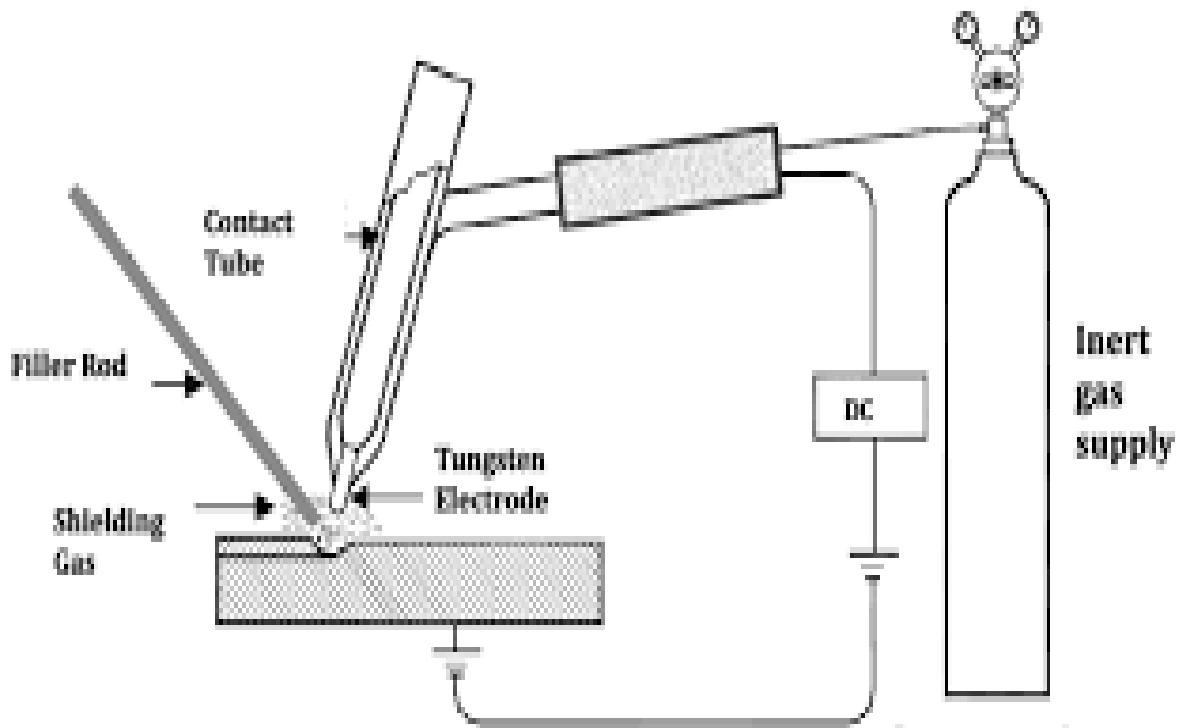

**Fig. 1 Schematic diagram of TIG welding**

## CHAPTER 2

### LITERATURE REVIEW

TIG welding is widely used for different types of metal & alloy and still lots of research work is going for better performance by TIG welding process.

**Krishnan et al. [1]** done experiment to analyze the microstructure and oxidation resistance at different regions in the mild steel weld by TIG welding. During welding process a sharp change in the microstructure due to complex thermal cycle and rapid solidification was observed. This micro-structure change also affects the mechanical properties and oxidation resistance of the mild steel weld. Autogenous TIG welding was performed on 12 mm thick mild steel with 200 A current, 19 V voltage and 100 mm/min welding speed. Finer grain size was obtained at weld metal and heat affected zone.

**Raj and Varghese [2]** predict the distortion developed during TIG welding of low carbon steel. In their study, have developed three dimensional finite element model like longitudinal, angular or transverse distortion. Distortion in welding produced due to non-uniform heating and cooling. To validate the model welding was performed with welding current 150 A, electrode gap 3 mm, gas flow rate 25 l/min, electrode diameter 0.8 mm and Argon as shielding gas. They concluded that, maximum distortion occurs at surface opposite to the weld and along X direction of weld compare to other twodirections.

**Abhulimen and Achebo [3]** performed experiments to identify the economical welding parameters using Response surface methodology (RSM) during TIG welding of mild steel pipe. Welding Parameters considered were gas flow rate 25 to 30 l/min, welding current 130 to 180 A, arc voltage 10.5 to 13.5 volt and argon as shielding gas. Results showed that, by using TIG

welding of mild steel maximum tensile and yield strength of 542 MPa and 547 MPa was achieved respectively.

**Mishra et al. [4]** have done comparison of mechanical properties between TIG and MIG welded dissimilar joints. Mild steel and stainless steel dissimilar material joints are very common structural application. These dissimilar joints provide good combination of mechanical properties like corrosive resistance and tensile strength with lower cost. Welding parameters considered for MIG welding were welding current 80-400 A and voltage 26-56 volt. TIG welding was performed with 50-76 A current & 10-14 volt voltage. TIG welded dissimilar joint provide better tensile strength because of less porosity. Both dissimilar joint have best ductility & yield strength for TIG and MIG welding.

**Fujii et al. [5]** developed an advanced activated TIG welding method for deep penetration of weld joint. Maragani convection induced on the molten pool by surface tension gradient. In order to control Maragani convection small amount of oxidizing gas was used. Welding process done with welding current 160 A, welding speed 0.75 mm/s, electrode gap of 1mm and Ar-O<sub>2</sub> shielding gas. They observed that Maragani convection changes from inward to outward and weld shape become wide and shallow.

**Kuo et al. [6]** investigate effect of oxide fluxes during TIG welding of 6 mm thick dissimilar joint between mild steel and stainless steel. The CaO, Fe<sub>2</sub>O<sub>3</sub>, Cr<sub>2</sub>O<sub>3</sub> and SiO<sub>2</sub> fluxes were used in powder form. These powders were mixed with acetone to produce paint. Before welding a thin layer of flux was brushed onto the surface of the joint to be welded. TIG welding was performed with welding speed 150 mm/min, welding current 200 A and gas flow of 12 l/min. The result indicates that surface appearance of TIG welds produced with oxide flux formed residual slag. TIG welding with SiO<sub>2</sub> flux powder can increase joint penetration and weld to depth ratio.

**Vikesh et al. [7]** studied the effect of activated flux on TIG welding process. They focused on the effect of penetration in mild steel by TIG welding process. Compare to other arc welding process it having small depth of penetration. An activating flux powder is used to avoid this problem. Taguchi optimization is used to optimize welding process parameters using activating TIG welding method on mild steel. They observe from experimental result that improves in depth of penetration at weld zone with increase weld current. Depth of penetration is inversely proportional to the travel speed.

**Pal and Kumar [8]** studied the effect of activated TIG welding on wear properties and dilution percentage in medium carbon steel welds of 12 mm thick plate.  $\text{TiO}_2$  and  $\text{Cr}_2\text{O}_3$  fluxes were used in powder form. Flux powder was uniformly mixed with acetone and brushed onto the surface of joint to be welded. DC current and straight polarity was used with constant welding speed. A single pass TIG welding was performed with 180A welding current. The result indicated that  $\text{TiO}_2$  flux coated weld increased the dilution on base metal as compare to  $\text{Cr}_2\text{O}_3$  flux coated weld.

**Nayee et al. [9]** studied the effect of oxide based fluxes on metallurgical and mechanical properties of weld joint. Tungsten inert gas welding process is used to produce welds between 6mm thick mild steel and stainless steel plate with activating flux. In this investigation  $\text{ZnO}$ ,  $\text{TiO}_2$  and  $\text{MnO}_2$  powder were used. Welding process performed with welding current 200 A, arc voltage 12.5 V and welding speed of 55 mm/min. Highest width to depth ratio get under  $\text{TiO}_2$  and  $\text{ZnO}$  fluxes compare to conventional TIG welding process. Among all three fluxes  $\text{TiO}_2$  shows lowest angular deformation.

**Ruckert et al. [10]** show that during TIG welding process application of activated fluxes improve weld penetration and process competitiveness. They summaries the investigations on

TIG welding of stainless steel, plain carbon steel, aluminum and titanium using activating flux. Welding process performed with 150 A & 175 A current and 15 cm/min welding speed. It was revealed that fluxes based on fluorides contribute to enhanced weld penetrations of titanium and SiO<sub>2</sub> flux for stainless steel, plain carbon steel and aluminum. The importance of flux homogeneity, flux composition and profile are shown to be primordial in determining width to depth ratio of weld.

**Dhanda et al. [11]** done experiment to show the effect of activated fluxes on mild steel welds. Maximum 2 to 3 mm thick plates of stainless steel and carbon steel can be weld with TIG welding under autogenous mode. The activating flux welding process is considered as feasible alternative to increase process productivity. Grade 91 steel is used as a workpiece material. A TIG welding was applied on P91 steel in which oxide powders CaO, ZnO, Fe<sub>2</sub>O<sub>3</sub>, TiO<sub>2</sub>, MnO<sub>2</sub> and CrO<sub>3</sub> were used as flux material to produce a bead on plate weld. This method is responsible for increase in depth of penetration and also reduction in weld width. Heat input was increased with use of activated fluxes.

**Fujii et al. [12]** done comparative study of strength characteristics of mild steel and cast iron weld using various welding process. An important contribution would be made to fabrication industry through capability being available for joining of cast iron to mild steel using welding process. Selection of welding processes and consumables was based on the welding technologists and skilled welding operatives in industrial welding. Four commonly used welding processes (Gas welding process, metal arc welding process with a covered electrode, Metal Active Gas welding and TIG welding) were finally selected for production of specimens. The test specimens produced with metal active gas welding show good elongation and high tensile strength.

**Mahajan et al. [13]** studied the effect of mechanical arc oscillation on the weld metal grain structure in mild steel using TIG welding. For same welding parameters columnar grain were observed in the weld without arc oscillation and smaller sized grain observed in weld with arc oscillation. Mild steel weld grain structure is affected by various welding parameters like arc voltage, welding current, welding speed and types of welding process. It was found that higher strength for weld with oscillation compared to without arc oscillation on weld. Hardness of weld specimen with arc oscillation was less than without arc oscillation on weld.

**Pasupathy and Ravisankar [14]** have done optimization of tungsten inert gas welding parameters using Taguchi technique for dissimilar joint of low carbon steel and aluminium. Welding current, welding speed and distance between work material and electrode were used as input parameters in three level for optimization of the process.

**Dye et al. [15]** observe quasi steady state phase evolution and transient stresses produced around the TIG welding torch in plain carbon steel during TIG welding process. The dimensions of tubes were 203 mm in diameter and 3.2 mm in thickness. The TIG welding process performed under autogenous mode and DCEN condition. Input welding parameters were 35 A current, 14 V voltage & 0.5 mm/s welding speed. This technique is also applied to identify materials where stress state is required to be modified for minimize cracking. Experiment shows that compression in HAZ just behind TIG welding torch is observed.

**Vasiri et al. [16]** done experiment to determine arc efficiency of TIG welding by calorimetric method. A water cooled calorimeter was designed to measure arc efficiency. TIG welding process was performed using two polarities (DCEN and DCEP) with 5 mm arc length on mild steel. The principle of water cooled method is based upon heat transfer from workpiece to water. TIG welding was done with 250 A current DC power source. Experimental results show that arc

efficiency decreases with increment in arc length. Arc efficiency is not affected by gas flow rate. It is also independent from welding current.

**Meng et al. [17]** performed experiment to obtain high welding speed by using TIG and metal active gas (MAG) hybrid arc welding of mild steel. The effect of welding parameters on weld appearance and speed were analyzed through orthogonal experiment. Mechanical properties and microstructure of the welded specimen were tested. These specimens were compared with conventional MAG weld. Hybrid arc welding process was performed with welding current 350 A, gas flow rate of 9.5 l/min on 2.5 mm thick mild steel plate. Hybrid arc welding achieve 3.5 m/min welding speed under condition of high quality of weld. Mechanical property of hybrid arc weld is greater than conventional MAG weld.

**Zuber et al. [18]** performed experiment to investigate the effect of oxide based flux on 8 mm thick austenitic stainless steel plate. They show the effect on welding distortion, hardness value, ferrite number and depth of penetration on weld. SiO<sub>2</sub> flux is used in powder form mixed with acetone and paint of bead plate. The experimental result showed that this technique can increase depth of penetration at weld zone. Hardness value of weld increased due to the high temperature of joint. Welding distortion was more under autogenous mode but with the application of flux angular distortion of weld sample seems to be reduced.

## **2.1 Objectives of research**

- To perform autogenous TIG welding of 5 mm thick mild steel plate (AISI 1020) without using any filler rod and study the effect of welding current and welding speed.
- To study the weld depth and width and micro structure of the weld area obtained after TIG welding for different welding condition
- To study the effect of various welding parameter like arc voltage, welding current and

welding speed.

- To perform TIG welding of 5 mm thick mild steel plate using a layer of TiO<sub>2</sub> coating (activated flux).
- To perform TIG welding of 5 mm thick mild steel plate by maintaining different gap between the plates to be welded.
- To measure the tensile strength of the weld joint.
- To measure macro-hardness of welding zone.



## **CHAPTER 3**

### **METHODOLOGY**

For the present work total experiments were performed in three different phases

In first phase autogenous TIG welding of 5 mm thick mild steel plates were performed without using any filler rod at different welding current and scan speed condition to see the effect of welding & speed and to obtain a current and speed range for approximate welding.

In second phase TIG welding of 5 mm thick mild steel plate was performed after applying a layer of TiO<sub>2</sub> flux and compared the weld properties with the welding done without flux.

In third phase, TIG welding was performed by maintaining different gap between the workpieces to be welded and study the effect of this gap on the welding performance mainly weld bead geometry and tensile strength of the weld.

#### **3.1 Experimental setup**

For the present project work an autogenous welding set up has been developed to perform welding with a fixed velocity without the application of filler material. A movable vehicle is used to hold TIG torch. The distance between workpiece and torch tip will remain constant the welding process. The speed of movable vehicle is controllable and can be varied according to the requirement of the welding speed and amount of heat required. Figure 3 shows experimental setup for present work. The welding setup for autogenous TIG welding process consists following components:

1. Welding torch
2. Electrode
3. Power supply
4. Inert gas supply unit

5. Work holding device
6. Movable vehicle holding the welding torch
7. Rail Track



**Fig. 3 Experimental setup of TIG welding**

1. **Welding torch** – TIG welding torch is capable for both automatic and manual operation. The automatic and manual torches are similar in construction. The manual torch has a handle while the automatic torch normally comes with a mounting rack. The internal metal parts of a torch are made of hard alloys of copper or brass in order to transmit current and heat effectively. The size of the welding torch nozzle depends on the amount of shielded area desired. The main purpose of TIG torch is to carry the welding current and shielding gas to the weld. For present work a manual torch has been fixed with the movable tracker using clamp arrangement to make

it automated. Figure 4 shows welding torch of autogenous TIG welding setup.



**Fig. 4 Welding torch**

2. Electrode – A non consumable tungsten electrode is used in TIG welding process. The tungsten electrode held firmly in the center of the torch and around the electrode a constant flow of shielding gas. The electrode used in GTAW is made of tungsten or tungsten alloy due to its highest melting temperature among the pure metals. Tungsten electrode is surrounded by a gas nozzle. This gas nozzle is generally made of ceramic material. For present experiment 2.4 mm diameter tungsten electrode has been used.

3. Power source – A constant current power source is used for TIG welding process. Direct current with straight polarity is used for welding of mild steel plate. Work material is connected to the positive terminal of DC welding machine and negative terminal to an electrode holder, this welding condition is said Direct Current with straight polarity. The DC power supply used for TIG can be steady or pulsed. For present work DC power supply in steady condition has been used where current is fixed and consequently voltage can vary to maintain a stable arc.

4. Inert gas supply unit – A gas cylinder is used to supply Argon gas to the welding torch. Argon gas is supplied from gas cylinder with a suitable gas flow rate. Gas flow is controlled by regulator and valve. The purpose of supplying inert gas is to shield the weld zone in order to

protect it from atmospheric contamination which leads to welding defects. For present experiment gas flow in the range 12-15 l/min has been flown.

5. Movable vehicle – A movable setup is used to provide constant welding speed for TIG welding operation. This movable tractor is used to hold the welding torch. It also help in maintaining a proper gap between tip of the tungsten electrode and welded area of the workpiece. Manually it is difficult to maintain a constant weld speed and gap between electrode and workpiece. So with the help of a portable moving tractor welding speed and gap between workpiece and electrode can be easily controlled. Figure 5 shows a movable vehicle to hold the welding torch.

6. Work holding setup – It is used to hold the workpiece material. Proper clamping is require to hold the workpiece during welding process, so that during heating and cooling workpiece should not bend. Further if welding done by keeping the workpiece directly on metal plate heat will flow by conduction method and does not concentrate in the welding zone. Therefore work holding device designed in such a way that just below the weld zone of plate some gap is maintained. Figure 6 shows setup of work holding device.

7. Rail track – Vehicle is move over this rail track in a straight path. Rail track is properly clamped by C clamp with the table.

## CHAPTER 4

### EXPERIMENTATION

#### 3.2 Single pass autogenous TIG welding on Mild steel plate

In this phase of experiment, to study the feasibility of autogenous welding on 5 mm mild steel plate, TIG welding has been performed without using any filler rod. 5 mm thick mild steel plates were cut in 50 mm x 50 mm dimension with the help of band saw. The edges to be welded were grinded with surface grinding machine, so that proper contact is possible between the plates to be joined. Other surfaces were also polished with emery paper (silicon carbide) to remove all impurities from the surface and to provide require surface finish.

After the sample preparation mild steel plates were fixed in the work holding device with proper clamp through bolts. Direct Current (DC) with direct polarity (negative electrode and positive workpiece) was used to perform welding. Zirconiated tungsten electrode of 2.4 mm diameter was used as electrode. Three different current value and scan speed has been selected as shown in the table 5 and total 9 experiments were performed.

**Table 5 Welding parameters for autogenous TIG welding of mild steel**

Dimension of mild steel	50mm x 50mm x 5mm
Welding speed	3 mm/s, 3.5 mm/s & 4.3 mm/s
Arc voltage	15 – 16 V
Welding current	210A, 230 A & 250 A
Gas flow rate	12 l/min
Current type	DC (positive workpiece& negative electrode)
Distance between tip and weld center	3 mm
Shielding gas	Argon

**Table 6 Experimental planning for autogenous TIG welding of mild steel**

Exp. No.	Welding current (A)	Welding speed (mm/s)
1	210	3
2	210	3.5
3	210	4.3
4	230	3
5	230	3.5
6	230	4.3
7	250	3
8	250	3.5
9	250	4.3

Sample preparation for study the weld bead geometry

After performing the TIG welding of mild steel plate, welded specimens were cut at the perpendicular to the weld scan direction with the dimension of 20 mm x 10 mm for taking optical microscope image of the weld zone. These welded specimens were cut with the help of wire electro discharge machine. After cutting the samples, polishing & chemical etching were performed at the weld cross section, before taken the optical image. Specimens were prepared by usual metallurgical polishing method using different grit size SiC polishing paper and subsequent diamond paste polishing. Nital solution consist of ethyl alcohol (97%) and conc. HNO<sub>3</sub> (3%), has been used for etching the weld cross section by dipping the polished surface in it for 10 sec. Melting depth or weld penetration was checked for each weld sample from the change in microstructure using an optical microscope.



**Fig. 9 Universal Testing Machine (UTM)**

### **3.3 TIG welding process with TiO<sub>2</sub>Flux**

TIG welding provides high quality weld and good weld bead surface. However, compare to other arc welding processes like plasma arc welding and submerged arc welding, TIG welding exhibit low penetration/melting depth in the workpiece. Therefore, it is required to improve the penetration/melting depth of TIG welded joint. This can be done with the help of inorganic powders generally called ‘Activated flux’. Applications of activated fluxes in various arc welding process for ferrous, non-ferrous and dissimilar materials gives higher penetration

compared to the welding done without using flux. The presence of flux narrow the arc concentrated energy in to a small area and reduces surface tension of the molten pool. This results in increases the depth of penetration of the weldjoint.

Activated flux is prepared using single component of any oxides (Cao, Fe<sub>2</sub>O<sub>3</sub>, TiO<sub>2</sub>, Zno, MnO<sub>2</sub> and Cr<sub>2</sub>O<sub>3</sub>) in powdered form or mixture of these powders. Activated flux then added in a liquid solvent like acetone of 5 to 10 ml of the flux powder and stirred to make it has homogenous paste, ready to be applied on the weld surfaces. A coating approximate 0.1 mm thick was applied to the surface of strip using a paint brush (10-12 mm) width prior to the welding.

**Table 8 Welding parameters for TIG welding of TiO<sub>2</sub>flux coated mild steel**

Dimension of mild steel	50mm x 50mm x 5mm
Welding speed	3mm/s, 3.5 mm/s and 4.3 mm/s
Welding current	250 A
Arc voltage	145– 16 volt
Current type	DC (positive work piece& negative electrode)
Distance between tip & weld center	3 mm
Gas flow rate	12 l/min
Shielding gas	Argon
Activated flux	TiO <sub>2</sub>
Electrode diameter	2.4 mm

### **3.4 TIG welding of mild steel by varying gap between work pieces to be welded**

It has been observed from the previous experiments that, during autogenous TIG welding of thick mild steel plates either using flux or without flux, when plates are kept side by side and no gap provided between them, the depth of penetration or melting depth is limited to a certain value and molten material does not flow towards the bottom side of the joint. It is found from the



literature, that during welding using filler rod, for the flow of molten material proper grooving is provided or some gap is maintained between the plates to be weld. Therefore, in this work, in order to increase the depth of penetration in weld, TIG welding was performed by maintaining a gap between the workpiece to be welded. An attempt has also been made to study the effect of gap between the plates during autogenous TIG welding of mild steel for using no fillerrod.

In conventional TIG welding method depth of penetration is low at weld zone in thick mild steel plate. For the purpose of increment of the depth of penetration in weld TIG welding was performing with maintain gap between workpiece. All this results increase in depth of penetration. The 100 mm length welds were obtained along welding direction without application of wire or filler material. Total 9 experiments were performed and welding shown in table 9. Welding process done with constant speed and same value of fixed parameters as conventional autogenous TIG welding process.

**Table 9 Experimental planning for TIG welding of mild steel**

Exp. No.	Welding current (A)	Gap between workpiece (mm)
1	170	0.4
2	170	0.6
3	170	1.1
4	180	0.4
5	180	0.6
6	180	1.1
7	190	0.4
8	190	0.6
9	190	1.1

## CHAPTER 5

### RESULTS AND DISCUSSION

#### 4.1 Welded specimen performed by conventional autogenous TIG welding

Figure 11 shows TIG welded specimens performed with three different welding current and welding speeds.




**Fig. 11 Welded specimens performed with 3 different speed and current setting by conventional autogenous TIG welding process**

Macroscopic inspection of the samples produced from 9 experiment clearly reveal that weld joints formed with 210A current for different welding speed didn't satisfy the requirements of the welding. Therefore, these particular samples were discarded for further study. The remaining samples were considered for further testing, which has been described below.

#### 4.1.1 Optical Image at weld zone by conventional autogenous TIG welding process

Fig. 12 shows optical microscopic image at cross section of weld zone by autogenous conventional TIG welding process performed with 230 A and 250 A welding current and three different speeds. The images show that, melting of the weld zone is not fully done for all different current and scan speed combination. Further, it is seen that, weld melt pool depth is larger for higher current (250 A). It is also seen that, as scan speed increase for a particular current value, melt depth reduce.

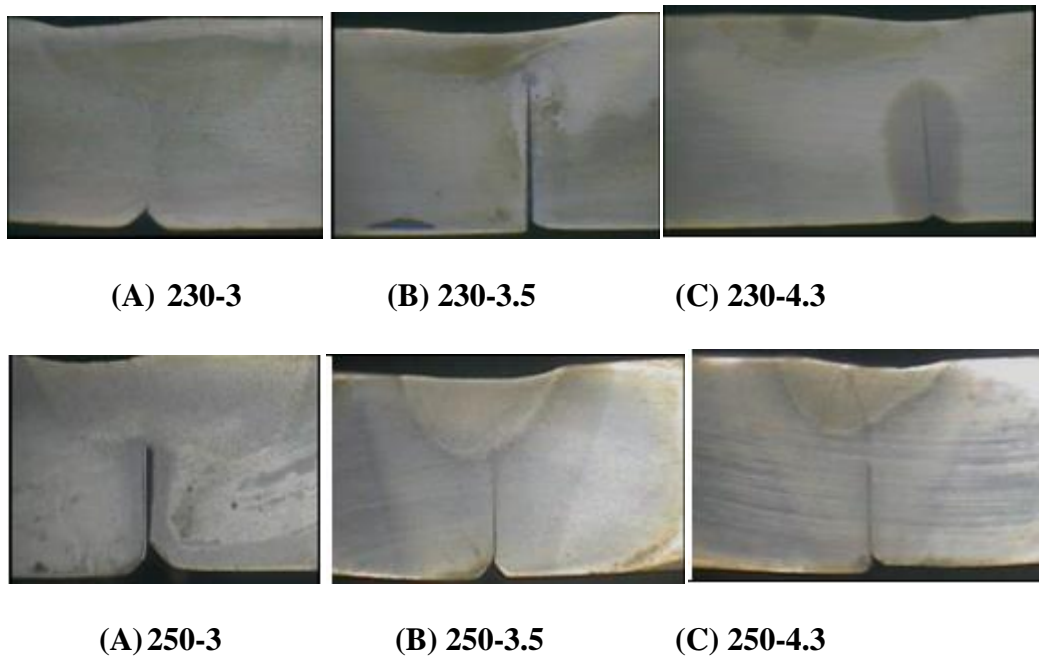


**Fig. 12 Optical microscopic Image at cross section of weld by conventional autogenous TIG welding process**

**4.1.2 Weld bead geometry at cross section of weld zone by conventional autogenous TIG welding**

**Table 10 Width and depth of weld zone of TIG welded sample by conventional TIG welding**


S.N.	Current(A)	Speed(mm/s)	Width(mm)	Depth(mm)
1	230	3	6.3	2.3
2	230	3.5	5.7	1.26
3	230	4.3	5.8	1.54
4	250	3	7	2.40
5	250	3.5	5.8	2.07
6	250	4.3	6.15	1.90

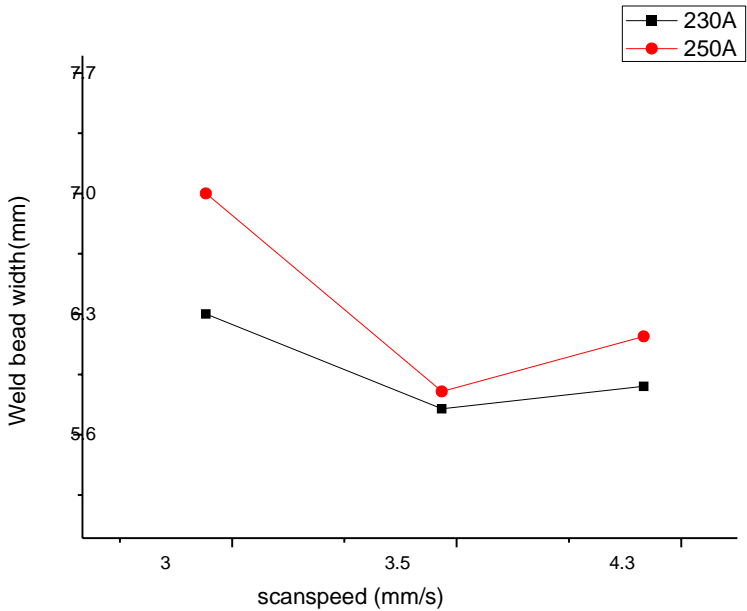

**Fig. 13 Variation of weld bead width against scan speed for different welding current**

Figure 13 shows the variation of weld bead width against scan speed for 230 A and 250 A welding current of welded specimen. The maximum welding width obtained at minimum welding speed and maximum current. It was normally observed that weld bead width increases

as current increases but decreases with increment in welding speed.

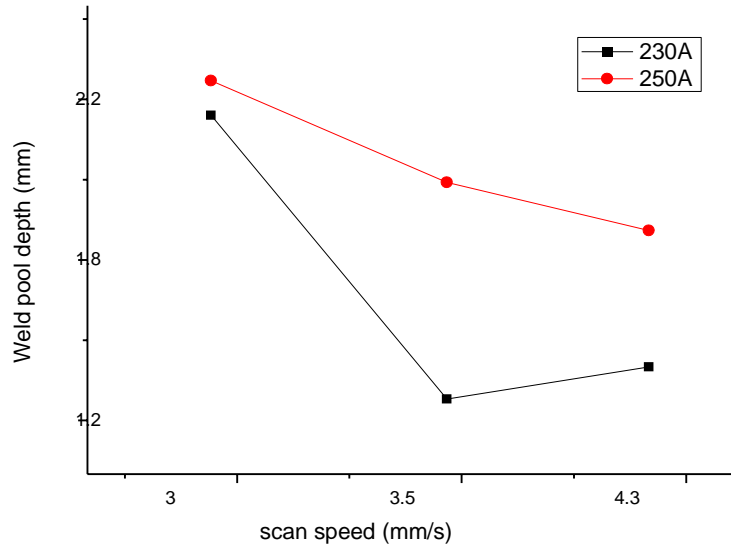

**Fig. 14 Variation of weld pool depth against scan speed for different welding current**

Figure 14 shows the variation of weld pool depth against scan speed for different welding current of TIG welded specimen. Low welding speed and high current provide high heat input to the workpiece, so the depth of penetration was maximum at this condition. The maximum weld pool depth was 2.40 mm, obtained at 250 A welding current and 3 mm/s scanspeed.

Depth of penetration obtained in the above experiment was still small for proper applicability of the welding technique. Hence, more literature was studied and it was established that, depth of penetration can be further improved if activated flux is used during the welding process. Based on this, experiments were conducted again with an addition of activation flux utilization.

#### **4.2 Welded specimens performed by activated TIG welding process**

It was clearly observed from first set of experiment and results, that combination of maximum welding current and minimum speed provide high heat input to the workpiece material. However, maximum depth of penetration was obtained at this condition. Second set of

experiment performed with the use of TiO<sub>2</sub> flux and 250 A welding current for three different welding speeds. TiO<sub>2</sub> activated TIG welding process performed with 250 A current and three different speeds shown in figure 15.



**Fig. 15 TIG welded specimen with TiO<sub>2</sub> flux at 250 A current**

#### **4.2.1 Optical Image at weld zone of specimen performed by activated TIG welding process**

Figure 16 shows optical microscopic image at weld zone performed by TiO<sub>2</sub> flux coated autogenous TIG welding process with 250 A current and different scan speed.



**(a) 3mm/s**

**(b) 3.5 mm/s (c) 4.3mm/s**

**Fig. 16 Optical microscopic Image at weld zone of TIG welded specimen with use of TiO<sub>2</sub> flux**

From the optical image it is observed that, melt pool depth is relatively larger for using TiO<sub>2</sub> flux, but still full penetration welding was not obtained. Further, for using TiO<sub>2</sub> flux on the melt pool zone some crack has been form. This crack may reduce the strength of the welding. Similar


observation was done by some other researcher for using activated flux in welding of different type of steel in TIG welding

#### 4.2.2 Weld bead geometry at cross section of weld zone by TIG welding with TiO<sub>2</sub> flux


**Table 11 Width and depth of weld zone of TIG welding with TiO<sub>2</sub> flux**

Sl. no.	Current (A)	Speed (mm/s)	Width (mm)	Depth (mm)
1	250	3	7.16	2.65
2	250	3.5	5.52	3.09
3	250	4.3	6.28	2.95

—■— 250 A

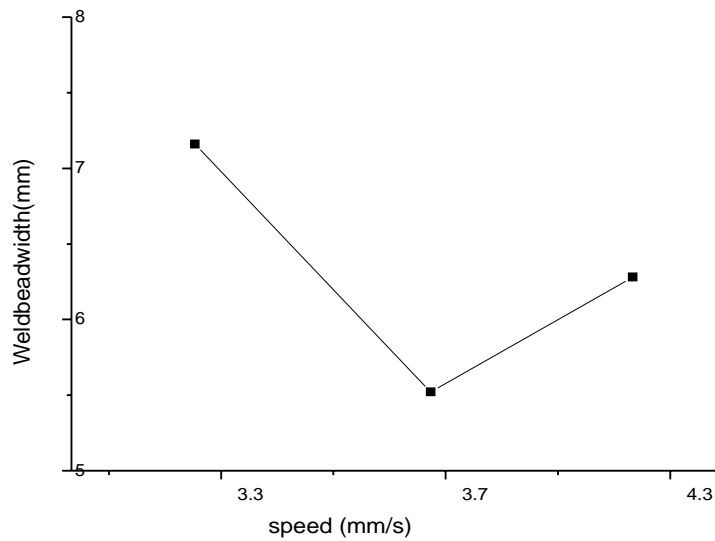

**Fig. 17 Variation of weld bead width against scan speed for 250 A welding current**

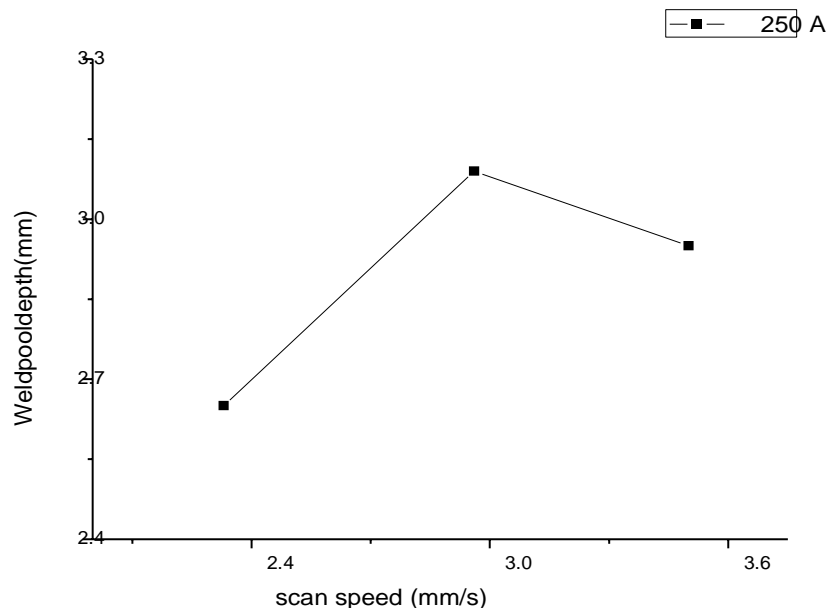

**Fig. 18 Variation of weld pool depth against scan speed for 210 A welding current**

Fig. 17 shows the variation weld bead width against scan speed for 250 A welding current of TiO<sub>2</sub> flux coated weld specimen. It was observed that welding width decreases with increment in welding current. The maximum weld bead width obtained at minimum welding speed.

Fig. 18 shows the variation of weld pool depth against scan speed for 250 A welding current of TiO<sub>2</sub> flux coated weld specimen. At minimum welding speed high heat input provided to the workpiece material, so the depth of penetration is inversely proportional to the scan speed. The depth of penetration of workpiece decreases with increment in weldingspeed.

In normal welding condition generally at lower scan speed depth of penetration is increases due to high heat input, but for using activated flux (TiO<sub>2</sub>) add the upper surface of the plate most of the heat absorbed by the surface and at lower scan speed a wider melt pool is formed. As a result welding depth is reduced.

Table 12 indicates measurement value of depth of penetration for both without using flux and



with using flux TIG welded sample. It was observed that the higher depth of penetration obtained for flux coated sample.


**Table 12 Comparison of depth of penetration between without flux weld and with flux weld sample**

Sl. No.	Current (A)	Speed (mm/s)	Depth(mm) without flux	Depth (mm) with flux
1	250	3	2.40	2.65
2	250	3.5	2.07	3.09
3	250	4.3	1.90	2.95

With the application of flux, desirable results, i.e. increase in depth of penetration was obtained. However, it was seen that material was unable to flow and weld properly as no gap was maintained between the components to be welded. To further improve the welding technique and facilitate optimum flow of the material, it was decided to maintain a suitable gap between the components. Taking this condition into account, more experiments were conducted to study the effect of welding gap kept between the welding sub-parts on the output response. In this regard, it is relevant to mention that, no study was reported on the effect of gap maintained between the workpieces to be welded by autogenous TIG welding process.

**4.3 Welded specimens performed welding by varying gap between workpiece**


In this set of experiment, suitable gap between workpiece was maintained for proper flow of material towards the bottom of the joint. Figure 19 shows welded specimens of mild steel performed by three different current and gap between workpiece to be welded. No flux is used for this set of experiment to avoid any crack on the weld zone.

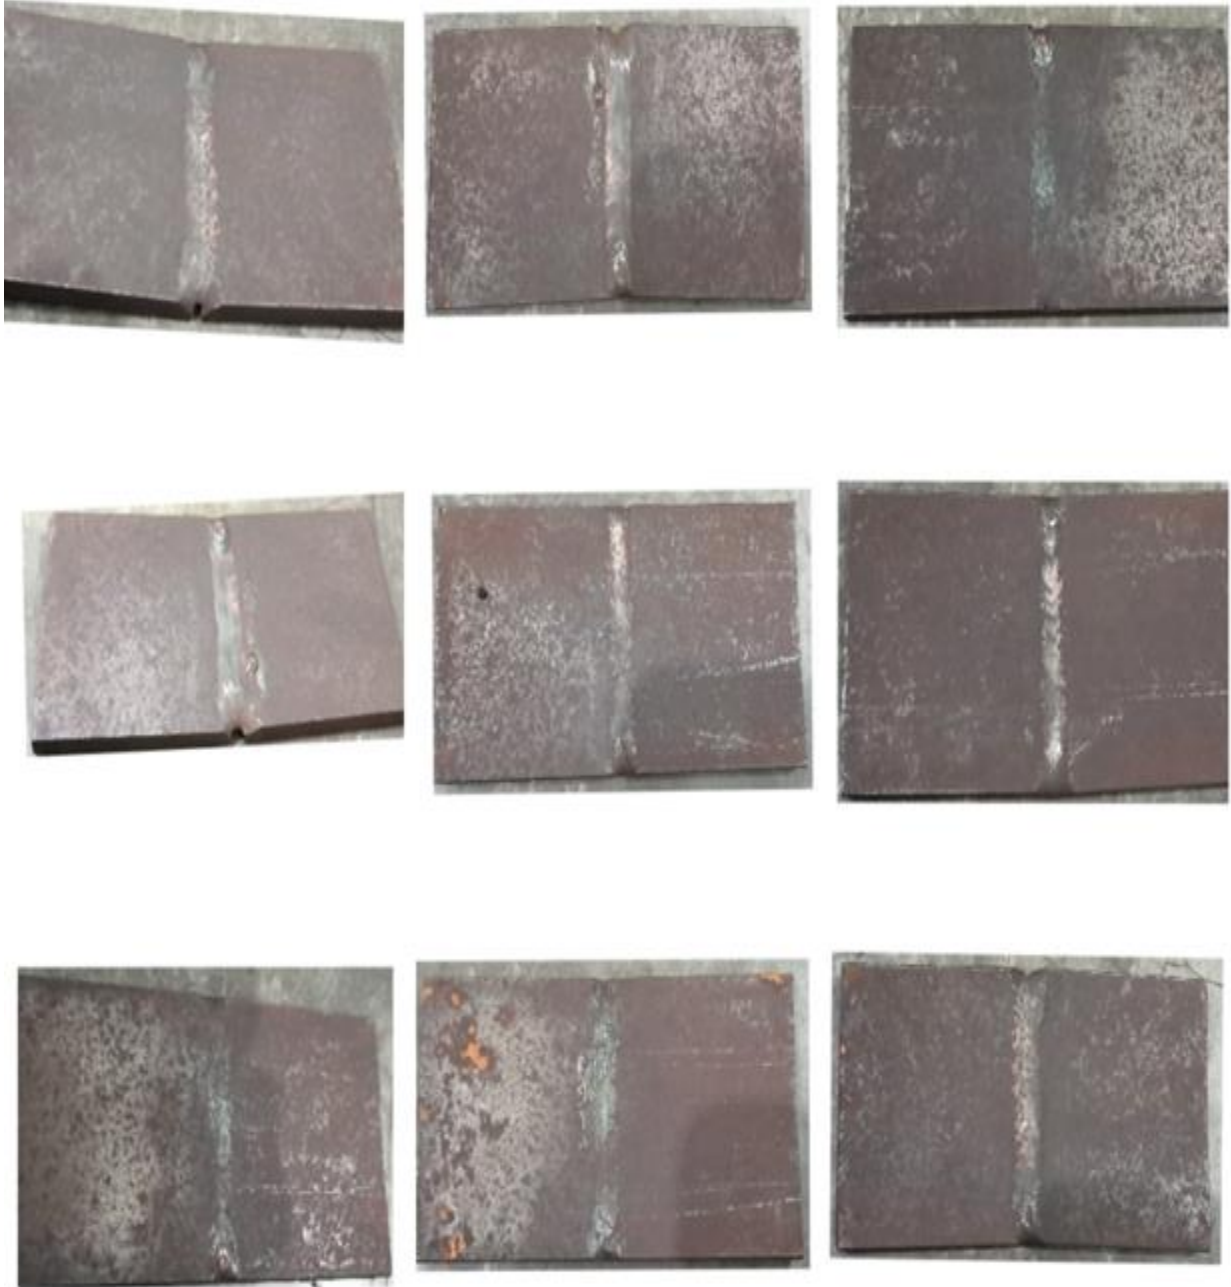

**Fig. 19 TIG welded specimens by varying gap between workpiece**

**Table 13 Measurement of width, depth and crater of welded sample at weld zone for different current and gap maintain between workpiece**


Sl. no.	Current (A)	Gap (mm)	Width (mm)	Depth (mm)	Crater (mm)
1	170	0.4	5.85	2.26	0.29
2	170	0.6	6.05	2.83	0.4
3	170	1.1	6.2	4.21	0.51
4	180	0.4	6.37	2.47	0.42
5	180	0.6	6.13	3.05	0.76
6	180	1.1	6.5	4.88	0.9
7	190	0.4	6.52	3.46	0.71
8	190	0.6	6.34	4.61	0.86
9	190	1.1	6.94	4.98	0.98

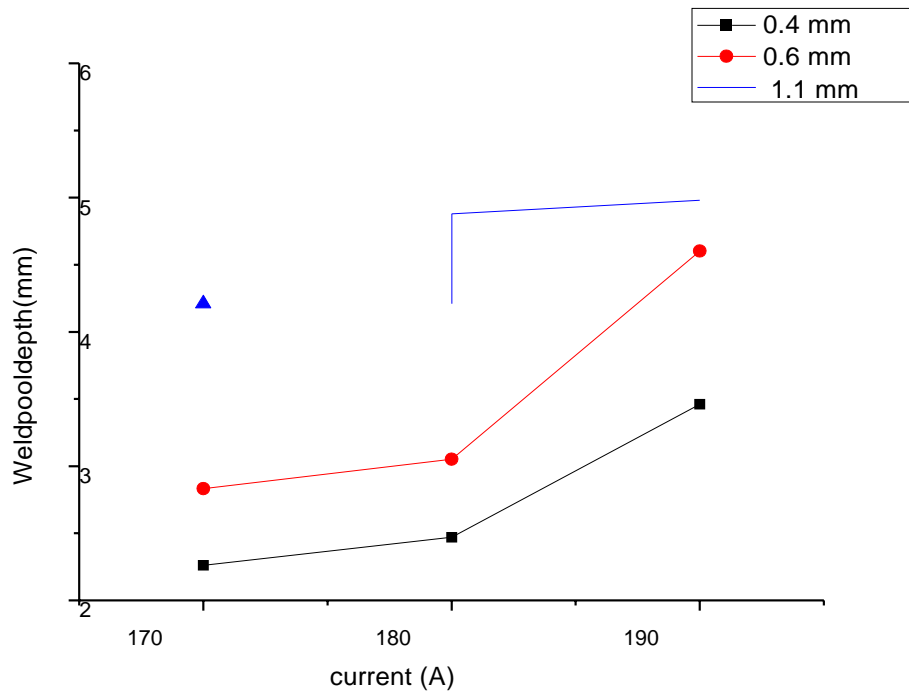

**Fig. 21 Variation of weld pool depth against welding current for different gap between**

**Workpiece to be welded**


Figure 21 indicates the variation of weld pool depth against welding current for different gap between workpiece to be welded. It has been observed that with the increase in current, weld pool depth increases. Current is directly proportional to the heat input according to relation  $H=I^2RT$ . So when current increases heat input increase and it melts the material and flows down in the gap, leading to the melting of adjacent layer of material thereby increasing the depth of penetration. The maximum depth of penetration was observed at 200A current in all the three gap condition.

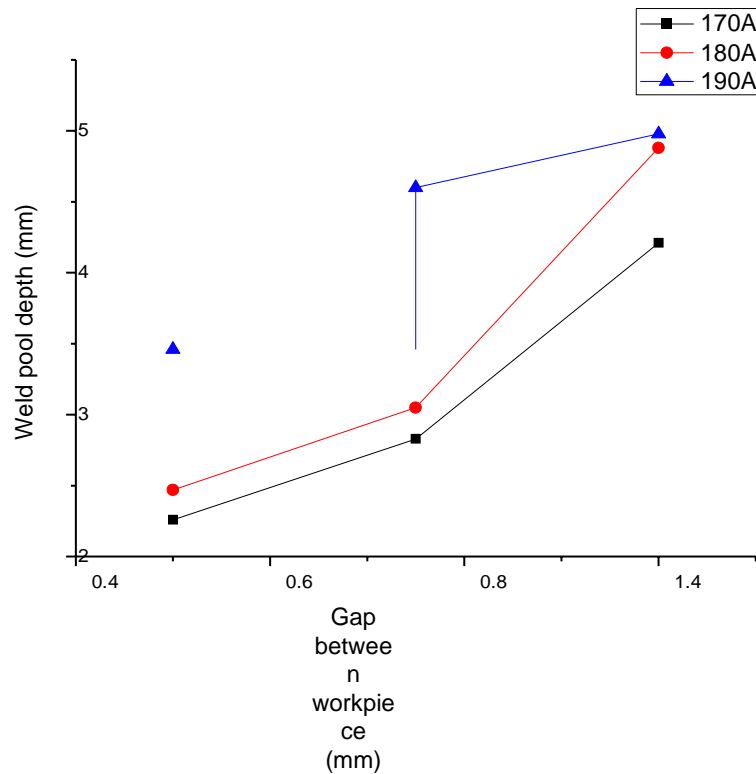

**Fig. 22 Variation of weld pool depth against gap between workpiece to be welded for different welding current**

Fig. 22 represents the variation of weld pool depth against gap between workpiece to be welded for different welding current. To enhance proper welding operation, the gap between two metals

should be neither too small nor too large. When welding was done without any gap the molten material did not get any space to flow and only convective metal flow within the melt pool occurred, that restrict the depth of penetration. However, molten material can flow within the gap and reach to bottom portion when a proper gap was maintained. The maximum depth of penetration is observed at 1 mm gap between workpiece to be welded.

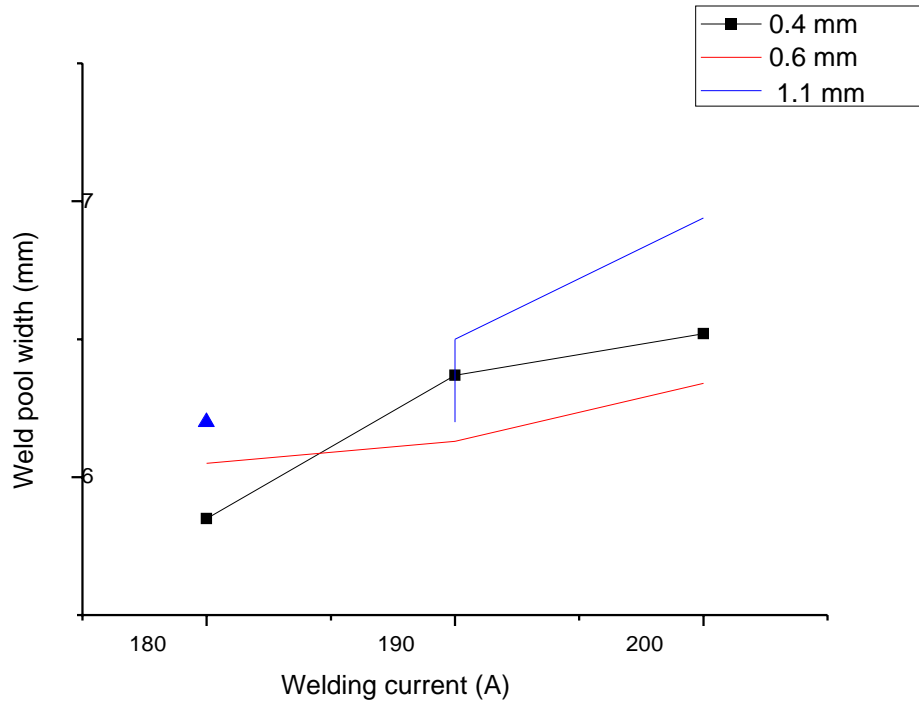


**Fig. 23 Variation of weld bead width against welding current for different gap between workpiece to be welded**


Fig. 23 shows the variation of weld bead width against welding current for different gap between workpiece to be welded. From the figure it can be seen that the value of welding width is increased with increment in applied welding current. Because of high current, crater was formed and welding width was large. The maximum welding width in this experiment was 6.94 mm at 200 A current.

Fig. 24 shows the Variation of weld bead width against gap between workpiece to be welded for

different welding current. From the graph it can be clearly seen that width increases as the gap increase. As gap was varied in this experiment ( 0.5 mm, 0.75 mm and 1 mm), this gap value is also contribute in the increment of width of the welded zone.

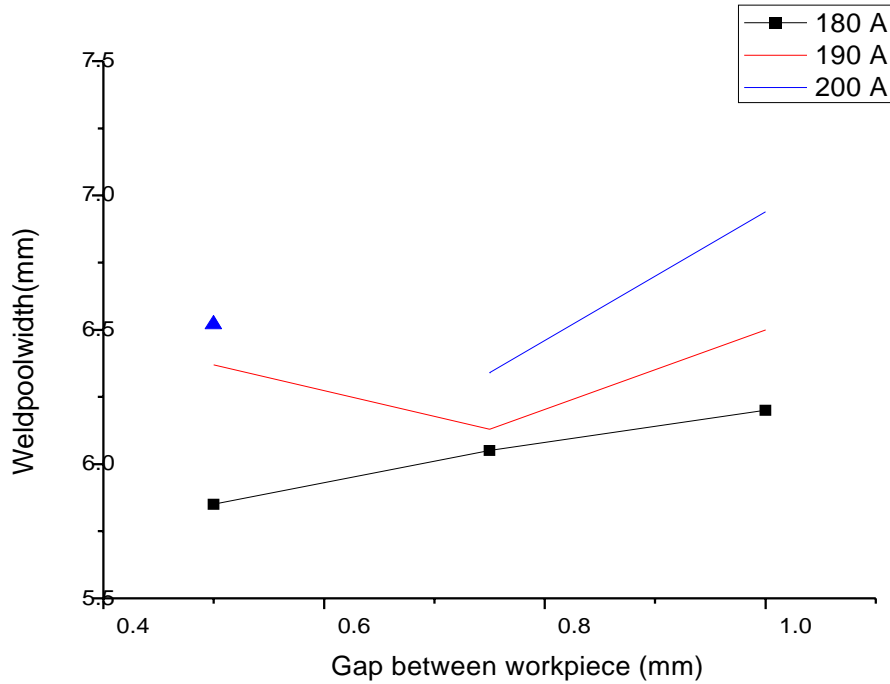


**Fig. 24 Variation of weld bead width against gap between workpiece to be welded for Different welding current**

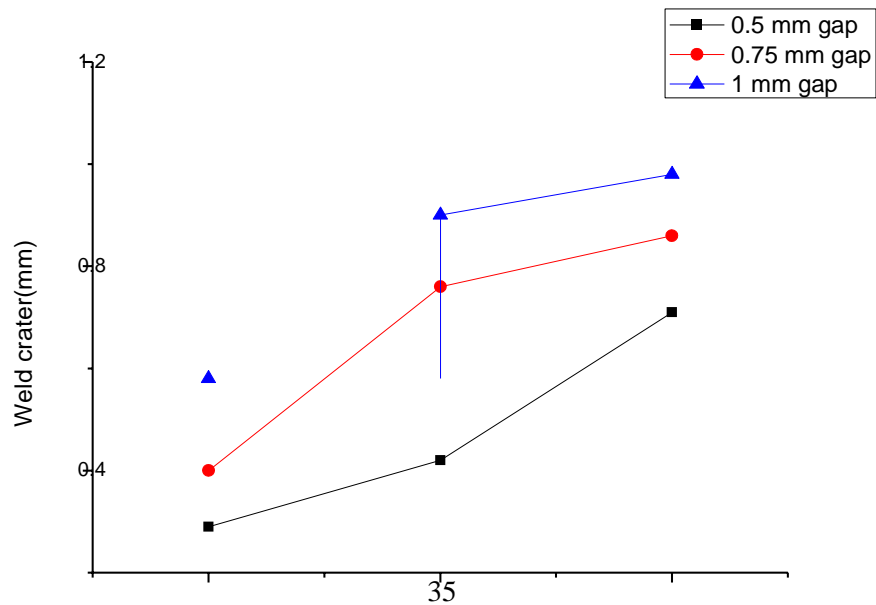

180                      190                      200  
current (A)

**Fig. 25 Variation of weld crater against welding current for different gap between workpiece to be welded**

Fig. 25 shows the Variation of weld crater against welding current for different gap between workpiece to be welded. It was observed that with the increase in current, crater increases at constant gap. At high current due to high heat input to the workpiece some amount of material from the top surface evaporated. Further flow of material within the gap make a concave surface on the workpiece. This is called crater in welding. As current increase this crater depth increases.

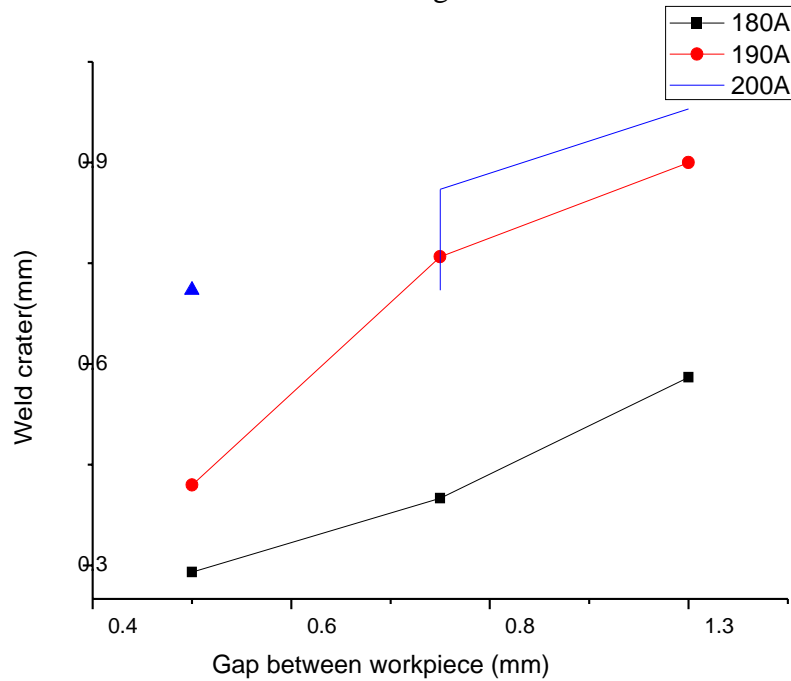

**Fig. 26 Variation of weld crater against gap between workpiece to be welded for different welding current**

Fig. 26 shows variation of weld crater against gap between workpiece to be welded for different welding current. In present work no filler material has been used and also maintained gap between workpiece. When the material melts, it fills up the gap between the workpiece. It was

observed that with the increases in gap volume of void space between two welding workpiece also increases.

#### 4.4 Tensile testing

In order to compare the strength of the welding joint at different welding conditions, tensile testing of welded specimen was performed using UTM. From previous two set of experiments it was established that higher depth of penetration was obtained at maximum current and minimum welding speed. Keeping this in mind, specimens with high current were more suitable for further analysis. Neither conventional TIG welded specimen nor activated TIG welded specimen provide better strength. The results of the test suggest that weld joint obtained are not strong enough which motivated the third set of experiments.

Fig. 27 shows specimen for tensile testing and Table 14 shows the maximum tensile strength value of weld with welding condition.


**Table 14 Tensile strength at weld joint by TIG welding of varying gap between workpiece**

Sl. No.	Welding current (A)	Gap between workpiece (mm)	Tensile strength (MPa)
1	170	0.4	115.95
2	170	0.6	225.21
3	170	1.1	264.54
4	180	0.4	319.10
5	180	0.6	346.38
6	180	1.1	501.173
7	190	0.4	442.98
8	190	0.6	395.45
9	190	1.1	617.22


Fig. 28 shows the variation of tensile strength against gap between workpiece to be welded for



different welding current of weld sample. It has been observed that the increase in gap between workpiece to be welded, tensile strength of weld workpiece increases. This is mainly due to the higher penetration of welding for higher welding gap maintain betweenworkpiece.

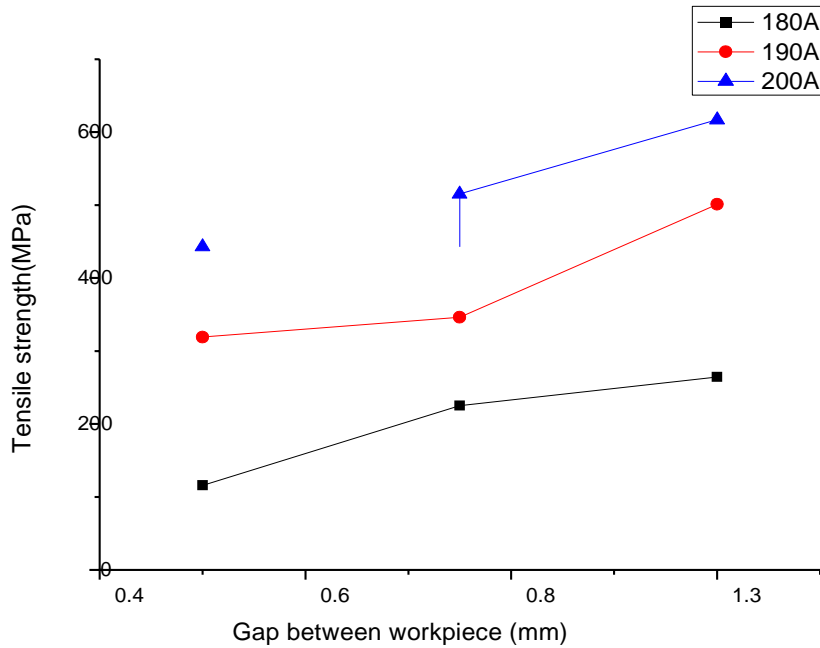

**Fig. 28 Variation of tensile strength against gap between workpiece to be welded for**

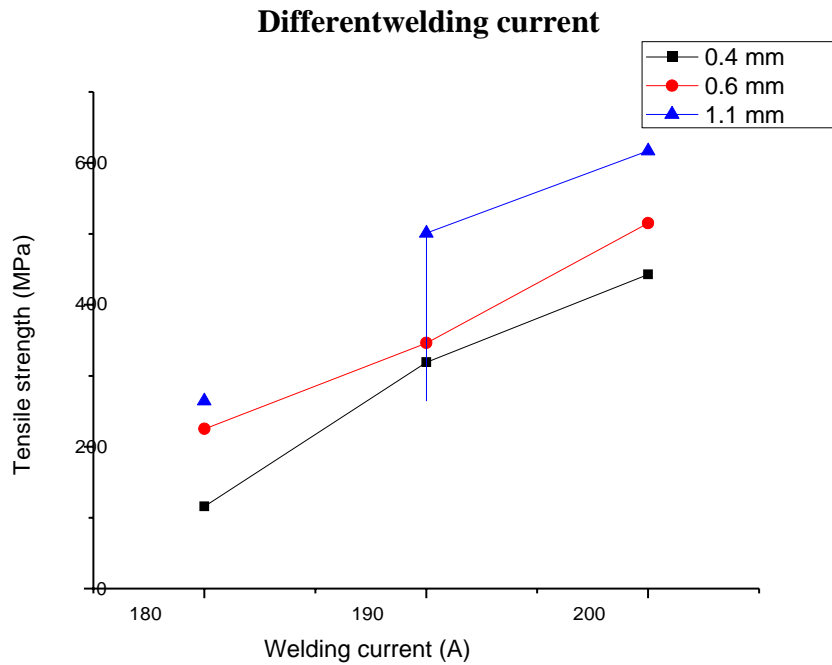

**Fig. 29 Variation of tensile strength against welding current for different gap between**

**Workpieceto be welded**


Similarly, Fig. 29 shows the variation tensile strength against welding current for different gap between workpiece to be welded. It has been observed that, with the increase in current tensile strength of weld workpiece increases. In this experiment autogenous for higher value of current heat input must be high. From the optical image it is seen that with the increase of current penetration depth increases. Higher penetration depth contributes for better strength.

#### 4.5 Vickers Hardness test

Hardness of the welded zone was measured for selective specimen at the cross section. Hardness test was performed using Vickers Hardness tester with 0.3 kgf minimum load capacity. Fig. 30 shows the hardness value at the welded zone, heat affected zone and base material for the sample processed with 200 A current and 0.75 mm gap. Table 15 shows Hardness value for some representative samples.

**Table 15 Hardness value for sample**

Sample No.	Welding current (A)	Welding speed (mm/s)	Gap between workpiece (mm)	Hardness value at molten metal Zone	Hardness value at heat affected zone	Hardness value at base material Zone
1	180	3	0.4	192.6 HV	158.5 HV	149 HV
2	190	3	0.6	198.5 HV	176.8 HV	146.4 HV

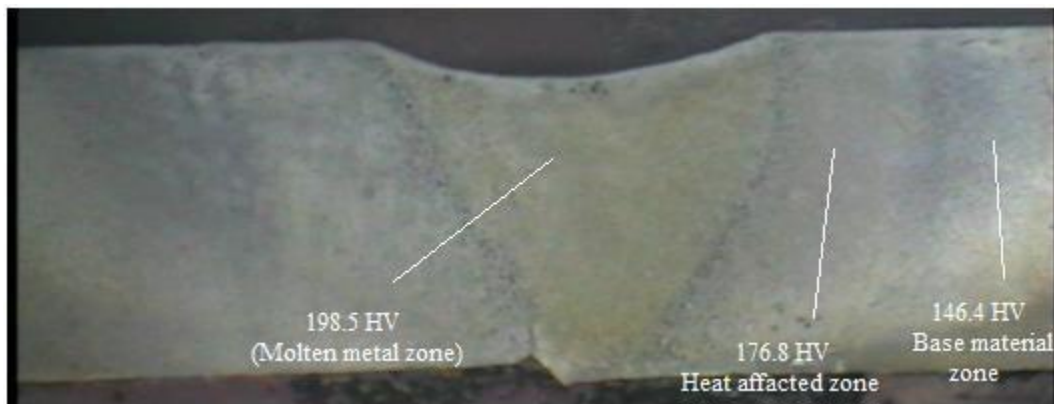

**Fig. 30 Hardness value of sample at weld zone processed with 200 A current and 0.6 mm gap**

It is observed from figure that hardness value decrease towards the base material zone. Average hardness values at molten metal zone for 180 A and 190 A current are 192.6 HV and 198.5 HV respectively. So it can say that approximate range of micro-hardness is 190 HV to 200 HV at molten metal zone for TIG welded samples.

## CHAPTER 6

### CONCLUSIONS

Findings of the present investigation can be summarized into following points

- The results of the conventional TIG welding process performed show that, maximum depth of penetration was obtained with parametric combination of minimum welding speed and maximum current.
- When the same procedure is repeated with additional utilization of TiO<sub>2</sub> flux, depth of penetration increases in comparison to the conventional welding, but some crack on the weld zone was observed for using flux.
- With constant welding speed, another set of experiments were done by maintaining a gap between workpiece to be welded. It is observed that, with a gap of 1 mm, defect- free welding with proper material flow obtained throughout the joint for higher welding current.
- Comparing the three methods of TIG welding, depth of penetration and tensile strength of weld joint is maximum when adequate gap is maintained between the components to be welded.
- From the graphs plotted, it can be inferred that welding width and depth increases with increase in welding current and gap maintained between the components to be welded.

## REFERENCES

1. **.K Abbasi**, "An Experimented Study on the Effect of MIG(metal inert gas) Welding parameter on the WeldBead Shape Characteristic." International diary of Engineering Science and Technology , ISSN-2250-3498, Vol.2, No. 4, August 2012.
2. **. S. R. Patil, C. A. Waghmare**, "optimization of MIG welding parameters for improving strength of welded joints". International Journal of Advanced Engineering Research and Studies, E-ISSN2249-8974.
3. **Sukhomay Pal et al**, studies optimisation of quality characteristic parameters in a metal inert gas welding process using grid based tabuchi method.
4. **P. Srinivasa Rao et al**, studies the effect of process parameter and mathematical model for the prediction of the geometry in first GMA welding.
5. **Ching-Been Yang & Chyn-Shu Deng and Hsiu-Lu Chiang**, Proposes progressive tabuchi natural network model which combines the method with the artificial neural network to construct and prediction model for a CO2 laser cutting experiment.
6. **A.S. Vaghl, S. N. Pandey**, " influence of process parameter on the mechanical properties of friction stir welding AA2014 – T6 alloy using Taguchi orthogonal array", International Journal of engineering science and emerging Technology volume 2, issue first ,PP 51-52 8 April 2012.
7. **S. Jannet, P. K. Mathews, R. Raja**, "comparatively investigation of friction stir welding and fusion welding of 6061 T6 and 508 3-0 aluminium alloy based on mechanical properties and microstructure", journal of achievements in materials and Manufacturing Engineering Volume 6 ,issue 2 ,December 2013.
8. **Chandresh N.Patel**, "Parametric Optimisation of Weld-Strength of Metal Inert Gas Welding(MIG) and Tungsten Inert Gas Welding(TIG) By Using Analysis of Variation and

GreyyRelationa Analysis.” International Journal of Research in Modern era Engineering and Emergging Technology, ISSN-2320-6586, Vol-1(2013), Issue: 3 April-2013.

**9. S.utkarsh et al.**“Experimental research of MIG welding for st-37 using design of experiment.” International Journal Advance Research in Science And Engineering , ISSN-2250-3153, Vol-4(2014)

**10. Ajit Hooda, et al.**“Optimization of mig welding process parameters to forecast optimum yield strength in AISI-1040.”International journal, ISSN-2278-0149, Vol. 1, No. 3, October 2012

**11. P. Neel et al.**’experimental research of MIG welding for (ST-37) using design of experiment(DOE).’ International Journals of Scientific and Research Publications, volume 4, Issue 5, May 2014, ISSN 2250-3153.

**7. Srivani Valluru et al.** “Investigation of Process Parameters during MIG Welding of AISI-1010 Mild Steel Plates” International Research Journal of Engineering and Technology (IRJET) e-ISSN: 2395 -0056

**8. Sindiri Mahesh, Velamala.Appalaraju**“ Optimization of MIG Welding Parameters for enhancing the Strength of the Welded-Joints” International Journal Of Innovation Technology And Researches.

**10. Manoj Singla et al.,**“ParametricOptimisation of Gas Metal Arc Welding(GMAW) Processes by Using “Factorial Design Approach”Journal of Minerals & Materials Characterisation& Engineering, Vol. 9, No.4, pp.353-363, 2010

**11. Pushendra Kumar Sharma et al.,** “Comparative research & Analysis Of Weld-Strengths Of Spot & fusion Laser Mig Welding On butt Joint” International Journal of Advancement in Engineering Research, 2012

**12. Biswajit Das, B. Debbarma, R. N. Rai, S. C. Saha**“Influences Of Process Parameter On Depth Of Penetration Of Welded-Joint In Mig Welding Process” International Journal of Researches in Engineering and Technology eISSN: 2319-1163.

**13. H.J. Park, D.C. Kim b, M.J. Kang b, S. Rhee,** “Optimizations technique of the wire feed rate during pulsation MIG welding of Aluminium-alloy sheets.” International Journal of Advanced Researches in Science And Engineerings, Volume No.3, Issue No.9, September-2014.

**14. Vikas Chauhan, et al.**"Parametric optimizations of mig welding for stainless steel (SS304) and low carbon steel using taguchi (DOE)design method." International Journal of Advance Technology & Engineering Researches (IJATER) 1st International Confernce on Research in Science, Engineering & Management (IOCRSEM 2014).

**15. S. Sivakumar and J.R. Vinod kumar,** “Experimental investigation on MIG welded mild steel.” International Journal of machine and construction engineering, volume 2, issue 1, March 2015, ISSN-2394-3025.

**16. Vineeta Kanwal, R S Jadoun,** "Optimization of MIG Welding Parameters for Hardness of Aluminium Alloys Using Taguchi Method." SSRG International Journal of Mechanical Engineering (SSRG-IJME), volume 2, Issue 6, June 2015, ISSN: 2348 – 8360.

**17. Amit Pal,** "MIG Welding Parametric Optimisation Using Taguchi Orthogonal Array And anova.." International Journal of Research assessment in Engineering Science and Technology, volume 4, Issue 1, April 2015, ISSN 2278-6643.

**18. Jay Joshi, Manthan Thakkar, Sahil Vora,**” Parametric Optimization Of Metal Inert Gas Welding And Tungsten Inert Gas Welding By Using Anova And Greyy Relational Analysis.” International journal of science and researches, ISSN 2319-7064.

**19. B. Mishra, RR Panda, D KMohanta,**”metal inert gas welding parameters optimization.”

International Journal of Multidisciplinary and Current Research, volume 2, Issue-June 2014, ISSN 2321-3124.

**20. Nur Azhani Abdul Razak, Shing Shiannng,**”Investigation Of Effect Of Mig Welding On Corrosion Behavior Of AISI-1010 Carbon Steel.” Journal of Mechanical Engineering and Science, Volume 7, December 2014, ISSN 2231-8380.

**21. Pranesh B. Bamankar , Dr. S.M. Sawant,** “study of the influence of procedure parameters on depth of penetration and weld-bead breadth in saw (submerged arc welding) process”, International Journal of Advanced Engineering Research and Studies, volume II issue IV, July-Sept., 2013/08-10.

**22.Rakesh Kumar, Satish Kumar** “ Study of mechanical properties in mild steel using metal inert gas welding” International Journal of Research in Engineering and Technology, Volume: 03 Issue: 04 Apr-2014



# EXPERIMENTAL OPTIMIZATION OF MILD STEEL ON TIG WELDING

Sheet Kumar<sup>1</sup>, Dr. Mohd. Shadab Khan<sup>2</sup>, Dr. Mohd. Anas<sup>3</sup>

<sup>1</sup>M.techStudent, Mechanical Engineering Dept, Integral University, Lucknow, UP India

<sup>2</sup>Associate Professor, Mechanical engineering Dept, Integral University, Lucknow, UP, India

<sup>3</sup>Associate Professor, Mechanical engineering Dept, Integral University, Lucknow, UP, India

\*\*\*

**Abstract** - Tungsten Inert Gas welding is also known as Gas Tungsten Arc Welding (GTAW), is an advance arc welding process become a popular choice when a high level of weld quality or considerable precision welding is required. However, the major problems of TIG welding process are its slow welding speed and limited to lower thickness material in single pass. In this work, autogenous TIG welding has been performed on 5 mm thick AISI 1020 mild steel plate without using any filler material. Wide range of welding current and scan speed has been tested for obtaining a full penetration welding. Activated flux has also been used to improve the weld depth. After performing welding by maintaining different gap between the plates to be welded, weld bead geometry and tensile strength of the weld has been investigated. It is observed that, by maintaining an appropriate gap full penetration welding of plate is possible which gives strength almost similar to base material.

## 1. INTRODUCTION

Welding is a process of joining two similar or dissimilar metals by fusion, with or without application of pressure and with or without use of filler metal. Weldability of the material depends upon various factors like the metallurgical changes that occur due to welding, change in hardness of material, in and around the weld and the extent of cracking tendency of the joint. A range of welding processes have been developed so far using single or combination of factors like pressure, heat and filler material used.

### 1.1 WORKING PRINCIPLE

In TIG welding process, the terminal is non-consumable and motivation behind it just to make a circular segment. The warmth influenced zone, liquid metal and tungsten anode are completely protected room air tainting by a cover of idle gas took care of through the GTAW light. Fig. 1 shows schematic graph of the working guideline of TIG welding process. Welding light comprise of light weight handle, with arrangement for holding a fixed tungsten terminal. In the welding light, the protecting gas streams by or along the terminal through a spout into circular segment area. An electric circular segment is made among terminal and the work piece material utilizing a consistent flow welding power source to deliver vitality and led over the bend through a segment of profoundly ionized gas and metal fumes. The electric curve produce high temperature and warmth can be engaged to melt and join two unique pieces of work piece.

## 2. LITERATURE REVIEW

TIG welding is widely used for different types of metal & alloy and still lots of research work is going for better performance by TIG welding process.

**Krishnan et al. [1]** done experiment to analyze the microstructure and oxidation resistance at different regions in the mild steel weld by TIG welding. During welding process a sharp change in the microstructure due to complex thermal cycle and rapid solidification was observed.

This micro-structure change also affects the mechanical properties and oxidation resistance of the mild steel weld. Autogenous TIG welding was performed on 12 mm thick mild steel with 200 A current, 19 V voltage and 100 mm/min welding speed. Finer grain size was obtained at weld metal and heat affected zone.

**Raj and Varghese [2]** predict the distortion developed during TIG welding of low carbon steel. In their study, have developed three dimensional finite element model like longitudinal, angular or transverse distortion. Distortion in welding produced due to non-uniform heating and cooling. To validate the model welding was performed with welding current 150 A, electrode gap 3 mm, gas flow rate 25 l/min, electrode diameter 0.8 mm and Argon as shielding gas. They concluded that, maximum distortion occurs at surface opposite to the weld and along X direction of weld compare to other two directions.

**Abhulimen and Achebo [3]** performed experiments to identify the economical welding parameters using Response surface methodology (RSM) during TIG welding of mild steel pipe. Welding Parameters considered were gas flow rate 25 to 30 l/min, welding current 130 to 180 A, arc voltage 10.5 to 13.5 volt and argon as shielding gas. Results showed that, by using TIG welding of mild steel maximum tensile and yield strength of 542 MPa and 547 MPa was achieved respectively.

**Mishra et al. [4]** have done comparison of mechanical properties between TIG and MIG welded dissimilar joints. Mild steel and stainless steel dissimilar material joints are very common structural application. These dissimilar joints provide good combination of mechanical properties like corrosive resistance and tensile strength with lower cost. Welding parameters considered for MIG welding were welding current 80-400 A and voltage 26-56volt. TIG

# **EXPERIMENTAL OPTIMIZATION OF MILD STEEL ON TIG WELDING**

By PAWAN BANSAL

---

**Submission date:** 29- Jun- 2022 12:48PM (UTC+0530)

**Submission ID:** 1849701625

**File name:** 1542240509 (SHEET KUMAR).pdf (2.22M)

**Word count:** 10367

**Character count:** 45196

# MTP1

---

## ORIGINALITY REPORT

---

**11%**

SIMILARITY INDEX

**8%**

INTERNET SOURCES

**5%**

PUBLICATIONS

**%**

STUDENT PAPERS

---